arXiv:1402.0901v1 [cond-mat.str-el] 4 Feb 2014

Cooperative effects of Jahn-Teller distortion, magnetism and Hund's coupling in the insulating phase of $BaCrO_3$

Gianluca Giovannetti,[1] Markus Aichhorn,[2] and Massimo Capone[1]

[1] *CNR-IOM-Democritos National Simulation Centre and International School for Advanced Studies (SISSA), Via Bonomea 265, I-34136, Trieste, Italy*

[2] *Institute of Theoretical and Computational Physics, TU Graz, Petersgasse 16, Graz, Austria*

We employ a combination of density functional theory and dynamical mean-field theory to investigate the electronic structure of the recently synthesized insulator $BaCrO_3$. Our calculations show that Hund's coupling is responsible for strong correlation effects, which are however not sufficient to turn the system insulating. A finite Jahn-Teller distortion lifting the orbital degeneracy is necessary to stabilize an insulating state with orbital ordering and consequent magnetic ordering.

PACS numbers: 71.27.+a, 71.30.+h, 75.25.Dk, 71.10.Fd

Strongly correlated materials are characterized by narrow valence bands arising from localized atomic orbitals. The reduced itinerancy of the carriers is the gateway that leads to the remarkable variety of phases and regimes observed in d- and f-electron systems. Usually strong electronic correlations are associated with the proximity of a Mott insulating state when the screened local Coulomb interaction U reaches a critical value U_c comparable with the bandwidth W of the system. For pure Hubbard-like interactions U_c would increase with the orbital degeneracy. However, in multi-orbital system, the Hund's exchange does not simply lead to a multiplet splitting, but it qualitatively affects the strength and the nature of the electronic correlations [1]. If the number of the electrons per correlated atoms is not equal to the number of orbitals (i.e., away from half-filling), the Hund's coupling increases U_c, but at the same time reduces the coherence of the system at intermediate interactions. This leads to a wide range of interaction parameters where the carriers are strongly correlated, but at the same time far from a Mott insulating state. This novel correlated regime is often referred to as a Hund's metal.

While fingerprints of Hund's metal physics have been reported to explain the bad metallic behavior of iron-based superconductors[2] and ruthenates[3], the interplay of Hund's correlations with electron-lattice coupling and the relationship with magnetic ordering have not been studied in detail. These effects are indeed strongly intertwined. For example, lattice distortions can lead to crystal-field splitting, which lifts the orbital degeneracy and may lead to orbital selective physics [4, 5]. In addition, as we will show below, crystal-field splitting can compete with Hund's coupling and Hund's metallicity, since it can induce orbital polarization, whereas Hund's coupling tends to make orbital occupancies equal. Furthermore, strong correlation physics is usually associated to the formation of local magnetic moments, which typically order in magnetic patterns which depend on both the interactions and the lattice structure, eventually leading to insulating behavior.

The perovskite compounds $ACrO_3$ (A being Ca, Sr, Ba) are a good playground to study this interplay. In those systems Cr has a nominal valence of 4+, with 2 electrons in the three-fold degenerate t_{2g} orbitals. Interestingly, such an electronic configuration is common to both metallic systems like (Ca,Sr)RuO_3 and insulating vanadates with formula RVO_3 (R being rare-earth), in which different orbital and spin orderings establish as a function of temperature [6].

Recently resistance measurements revealed $BaCrO_3$ to be insulating over a large range of temperature with a low-temperature gap of 0.38 eV [7], while there are conflicting evidences of metallic and insulator behaviors in $CaCrO_3$ and $SrCrO_3$ [8–11] and the general question of whether these compounds are metals or insulators is still under debate.

The compound with the smallest A-site ion in the series, $CaCrO_3$, shows an orthorhombically distorted $GdFeO_3$ structure in which the three Cr-O distances are comparable to those found in YVO_3 at room temperature [8] and is characterized by a C-type antiferromagnetic (AFM) magnetic structure [11]. The same C-type magnetism has been reported in $SrCrO_3$ in which however the octahedral-like $GdFeO_3$ distortions are suppressed [11]. Density-functional theory (DFT) calculations, including interaction effects within a DFT+U scheme, found $CaCrO_3$ [12] and $SrCrO_3$ [13] to be either weakly metallic or with a small gap, exhibiting C-type antiferromagnetism with orbital ordering.

To properly account for the delicate balance between inherent correlation effects and the tendency towards ordering, we use a combined approach based on DFT [14] and dynamical mean-field theory (DMFT) [15] which accurately treats the electronic correlations. Our study accounts for the insulating state of $BaCrO_3$, highlighting the role of Coulomb interactions U and J and their interplay with the lattice distortions.

We start our investigation with DFT calculations within the local-density approximation (LDA) for the tetragonal unit cell of $BaCrO_3$ using Quantum Espresso

[16] and Wien2K [17] packages. We build Wannier orbitals [18, 19] for the t_{2g} (xy,xz,yz) manifold of Cr, which define the basis where we consider the interaction effects. The Coulomb interaction within the t_{2g} manifold is taken in the Kanamori form

$$H_{int} = U \sum_{i,m} n_{im\sigma} n_{im\sigma'} + U' \sum_{i,m,m'} n_{im\sigma} n_{im'\sigma'} + \\ + U'' \sum_{i,m,m'} n_{im\sigma} n_{im'\sigma} \\ - J_h \sum_{i,m,m'} [d^+_{im\uparrow} d^+_{im'\downarrow} d_{im\downarrow} d_{im'\uparrow} + d^+_{im\uparrow} d^+_{im\downarrow} d_{im'\uparrow} d_{im'\downarrow}],$$

where $d_{i,m\sigma}$ is the annihilation operator of an electron of spin σ at site i in orbital m, and $n_{im\sigma} = d^+_{im\sigma} d_{im\sigma}$ is the density operator. Intra- and inter-orbital repulsions are given by U, $U' = U - 2J_h$, and $U'' = U - 3J_h$, and J_h is the Hund's coupling.

The values of U and J_h are determined on the basis of constrained random-phase approximation (cRPA) calculations that have been performed for the similar material $SrCrO_3$ [20], which gave $U = 2.7\,\text{eV}$ and $J_h = 0.42\,\text{eV}$. However the lattice parameters of $SrCrO_3$ are smaller with respect to those of $BaCrO_3$ by $0.1\,\mathring{A}$ so that we expect Cr d orbitals will be more localized in our compound. For this reason we use a slightly larger U keeping the same ratio J_h/U of $SrCrO_3$, namely $U = 3.25\,\text{eV}$ and $J_h = 0.505\,\text{eV}$. DMFT requires the numerical solution of a quantum impurity model including the local interactions. We use two implementations of LDA+DMFT, one using Exact Diagonalization (ED) [21, 22], the other one using continuous time quantum Monte Carlo (CTQMC) [19, 23, 24] to solve for the local Green's function of the impurity model implementing the conservation laws introduced in Ref.[25]. In order to study phases with magnetic and/or orbital ordering which spontaneously break the translational symmetry of the lattice we introduce a quantum impurity solver for each inequivalent Chromium site (or sublattice). This is equivalent to assume a local spin- and orbital-dependent self-energy with different values on each inequivalent site.

In the tetragonal unit cell of $BaCrO_3$ [7] (a=b=4.09 $\mathring{A}$, c=4.07 $\mathring{A}$) the small deviation from a pseudo-cubic perovskite structure lifts the orbital degeneracy of the t_{2g} orbitals, shifting the xy orbital to lower energy with respect to the degenerate (xz,yz) orbitals. The crystal-field splitting is 0.02 eV at LDA level. Non-magnetic LDA calculations describe $BaCrO_3$ as a metal, as can be clearly seen from the orbitally-resolved density of states shown in the inset of Fig. 1. All the three bands arising from the t_{2g} orbitals cross the Fermi level and they share a similar bandwidth of around 1.7 eV, similarly to the other compound of the same family SrCrO3 [20]. In particular the filling of the chromium bands confirms that the bandstructure is associated to Cr^{4+} ions and to a total filling of two electrons populating the three t_{2g} orbitals.

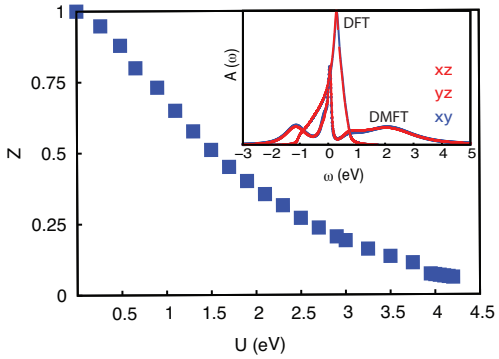

FIG. 1: (Color online) Quasiparticle weight Z as function of U fixing the ratio J_h/U fixed to the value 0.155 calculated with ED solver. Inset: Resolved orbital density of state of Wannier orbitals (DFT) and DMFT calculations.

Since the crystal field splitting is small compared to the bandwidth, the orbital occupancies in our calculations remain nearly degenerate being close to 0.66 electrons per orbital.

When we include the interaction effects in LDA+DMFT we expect a reduction of the effective bandwidth for the coherent motion of the carriers. The quasiparticle weight Z is a quantitative measure of this effect. A small value of Z is a fingerprint of a strongly correlated state, and a vanishing Z marks a Mott-Hubbard metal-insulator transition. In Fig. 1, we display our results for Z-which is independent on the orbital index-in the paramagnetic state as a function of interaction U, keeping the ratio of J_h/U fixed at the cRPA value 0.155.

The evolution of the quasiparticle weight Z displays the typical Hund's metal behavior, with a clear change of curvature around $U \approx 1.5\,\text{eV}$, separating a fast drop in the weak-coupling range from a flatter region for intermediate coupling in which Z is small but finite[26]. The Mott phase is indeed reached only at values of U close to 5 eV, significantly larger than the cRPA estimate.

Our calculations show that pure correlations effect, including the Hund's exchange, do not result in an insulating behavior that is experimentally observed in $BaCrO_3$ [7], and that other physical effects have to be taken into account. The most straightforward mechanism to turn the Hund's metal into an insulator invokes magnetic ordering, but this simple scenario seems to be ruled out by local-spin-density approximation (LSDA) calculations including an Hartree-Fock treatment of interactions (LSDA+U) which indeed stabilize a C-type magnetic structure that however remains metallic [7].

As mentioned above, another crucial effect to tune electronic correlations is the crystal-field splitting, which can be a consequence of a cooperative Jahn-Teller (JT) effect

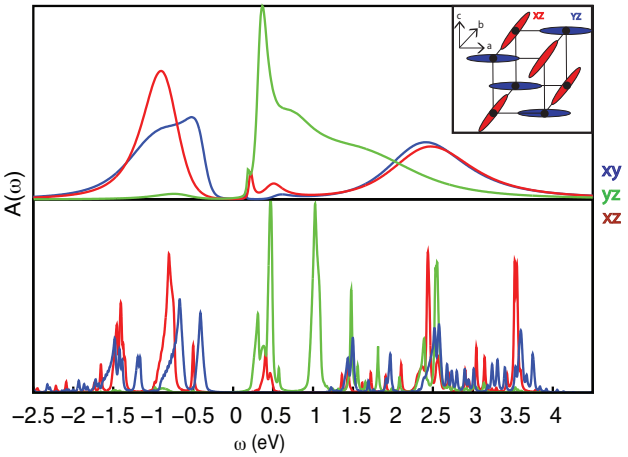

FIG. 2: (Color online) Resolved orbital spectral density for $U = 3.25\,\text{eV}$, $J_h = 0.505\,\text{eV}$ in G-type OO for $\delta = 0.17\mathring{A}$. Lower panel shows results using the ED solver, the upper panel results from CTQMC. Inset: Orbital arrangement (G-type OO) in the plane of tetragonal unit cell with the two inequivalent Cr-O distances.

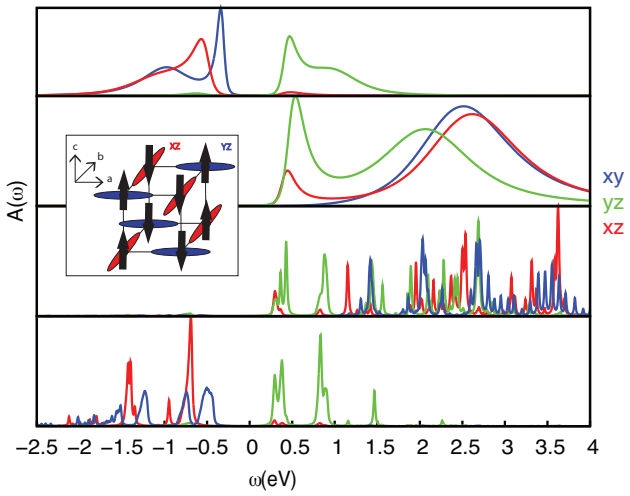

FIG. 3: (Color online) Orbitally-resolved spectral density for $U = 3.25\,\text{eV}$, $J_h = 0.505\,\text{eV}$ in G-type orbital ordering and C-type spin ordering for $\delta = 0.17\mathring{A}$. Lower two panels: Results using the ED solver for Majority/Minority spin channels. Upper two panels: Results from CTQMC for Majority/Minority spin channels. Inset: Spin (C-type AFM) and Orbital (G-type OO) arrangement in the plane of tetragonal unit cell with the two inequivalent Cr-O distances being.

[27] in which the lattice structure is distorted and the orbital degeneracy is lifted. It should be noted that a JT-driven splitting competes with the Hund's coupling concerning the orbital occupancies. Whereas the former tends to populate most the lowest-lying orbitals, the latter tends to distribute electrons equally among the orbitals to reduce the Coulomb repulsion by the intra-atomic exchange.

In electronically similar vanadates $LaVO_3$ and YVO_3 the JT distortion of the octahedra has indeed a dramatic influence on their electronic properties [28, 29]. The role of JT distortions in isoelectronic Chromium compounds has not been discussed to our knowledge, but LSDA+U calculations for $CaCrO_3$ predict orbital ordering in which one electron occupies the orbital with mostly xy character and the second one occupies the two combinations $xz + yz$ and $xz - yz$ in a staggered pattern [12], a configuration that would be further favored by JT distortions.

On the basis of the evidence for similar compounds, we can expect the JT effect in $BaCrO_3$ to give rise to two different possible orbitally-ordered configurations. First, we can have orbital ordering (OO) of the xz and yz orbitals in G-type fashion, where xz and yz orbitals alternate in all three spatial dimensions (see Inset Fig. 2). The second possibility is C-type OO, where xz and yz order in AF fashion in the ab plane, but ferromagnetically along the c-axis. We perform different LDA+DMFT calculations at different values of the short/long Cr-O distances (δ) with G-type and C-type OO as allowed by symmetry considerations. The results weakly depend on the value of δ and we present calculations for δ=0.17 $\mathring{A}$, which is a reasonable value for $BaCrO_3$ (See below).

The distortion of the oxygen sites splits the position of the energy levels of the (xy,xz,yz) orbitals: at a particular Cr site the xy lies between xz and yz orbitals which are higher and lower in energy by an amount of 0.05 eV with the two inequivalent Cr-O distances in the plane of tetragonal unit cell being the above mentioned $\delta = 0.17\mathring{A}$. The non-interacting orbital density of states shows three bands with nearly same bandwidth and shape of 1.8 eV with orbital occupancies being 0.79, 0.66 and 0.55 from the lower to higher energy level (xz,xy,yz), respectively. According to the symmetry of the crystal the occupancies of the xz and yz orbitals alternate in the a-b plane. The above results are essentially independent on the choice of C-type or G-type orbital ordering.

In this lattice configuration DMFT calculations enhance the occupancies of xz and xy orbitals with respect to yz upon increasing the electronic correlations as if the crystal-field splitting is effectively increased. Interestingly, the effect is realized via a strongly ω-dependent real part of the self-energy.

At $U = 3.25\,\text{eV}$ and $J_h = 0.505\,\text{eV}$ in the paramagnetic state the orbital occupancies of t_{2g} orbitals in the insulating solutions are 0.96, 1.0 and 0.04 for xz,xy,yz respectively, showing that correlations enhance the orbital correlations and result in almost perfect orbital ordering. The resolved orbital spectral density with the chosen values of U and J_h in Fig. 2 show that with the inclusion of a JT distortion the system turns insulating with a gap in good agreement with experimental values [7].

The relative orientation of orbitals on neighboring cations then determines the superexchange interactions between the unpaired d-electrons, which in turn determine the magnetic ordering patterns. The presence of a JT distortion is expected to give rise to a strong interplay between orbitals and spins [30].For perovskites with partially occupied e_g orbitals, such as cuprates [31] and manganites [32] or other Cr based compounds [33], the JT energy greatly exceeds the superexchange coupling between unpaired electrons, so that orbital and magnetic ordering temperatures are well separated. In the case of $BaCrO_3$, where only t_{2g} orbitals contribute to low-energy physics, we expect a weaker JT coupling and orbital and magnetic transitions could occur in the same temperature range. The orbital and spin orderings in $BaCrO_3$ might develop the same temperature-induced magnetization reversal [34] and different ordering temperatures [6] as in YVO_3 single crystal.

The calculated orbital occupancies establish that the lattice distortion triggers the magnetic ordering with a C-type (each spin is antiparallel to all others in the ab plane but parallel along the c axis) or G-type (every spin is antiparallel to all its neighbors) magnetic structure stabilized depending if a G-type/C-type OO is considered as expected from the Goodenough-Kanamori rule for superexchange [35]. In the magnetically ordered states the (xz,xy,yz) orbitals are filled by 0.95(0.0), 0.98(0.02), 0.03(0.02) electrons in the majority(minority) channels respectively. Once again, these populations do not depend on the precise nature of the ordered state. Magnetic ordering further increases the value of the gap by 0.1 eV as can be seen form the resolved orbital spectral density in Fig. 3 for the case of C-type magnetism and G-type OO.

We mention here that within LDA+DMFT we discard the possibility of a octahedral tilting with a $GdFeO_3$ type of distortion as in the case of $CaCrO_3$ crystal structure being the ionic radius of Ba larger as for Sr. Moreover a combination JT distortions and tilting of the oxygen octahedra allows by symmetry for many different space groups going beyond the scope of this work. There are only few attempts within LDA+DMFT schemes for fully microscopic investigations of the structural properties of strongly correlated electron materials such as lattice instabilities [36]. To further check our theoretical prediction we perform DFT+U calculations using the Wien2k package and an effective interaction $U_{eff} = U - J = 4$ eV. Note that interactions are here applied to atomic orbitals, and therefore the value for the Coulomb interaction is larger.

In Fig. 4 we show the total energy gain as function of the JT distortion for the non-magnetic, C-type magnetic structure within DFT and C-type magnetic structure within DFT+U, which confirm that the presence of a JT instability and the role of the Coulomb interaction in the insulating state of $BaCrO_3$. However, LDA+DMFT

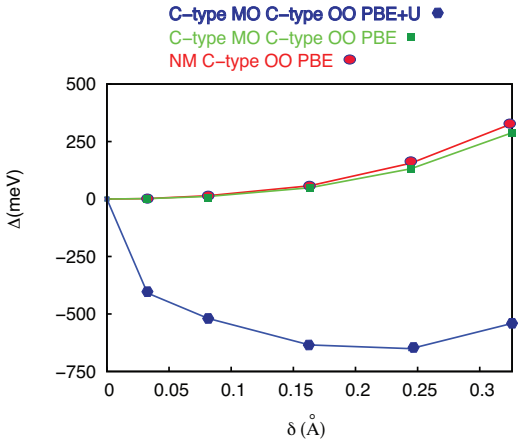

FIG. 4: (Color online) Total energy gain calculated within DFT in the nonmagnetic (NM) and C-type magnetic structure and within DFT+U in the C-type magnetic structure as function of the Jahn-Teller distortion δ (difference between long/short Cr-O bonds).

paramagnetic calculations provide an insulating solution for every finite JT distortion considered, while DFT+U requires the inclusion of magnetism to open the insulating gap.

In conclusion, we use an LDA+DMFT approach to study the electronic properties of the recently synthesized compound $BaCrO_3$, which is a non trivial insulator. We show that $BaCrO_3$, in its tetragonal crystal structure, would be a strongly correlated metal in which the degree of electronic correlations is tuned by the Hund's coupling. We predict that the insulating character arises from the combination of the above correlation effects and a Jahn-Teller splitting of the t_{2g} orbitals, which leads to orbital ordering and to a gap in good agreement with the experimental value. Magnetic ordering compatible with the Goodenough-Kanamori rule establishes in the JT distorted insulating state. Experimental investigations of the crystal structure of $BaCrO_3$ would be a direct test of our scenario.

We wholeheartedly thank S. Streitsov and L. de' Medici for precious discussions. GG and MC acknowledge financial support by European Research Council under FP7/ERC Starting Independent Research Grant "SUPERBAD" (Grant Agreement n. 240524). MA acknowledges support from the SFB VICOM subproject F04103. Calculations have been performed on the TU Graz *dcluster* and at CINECA (HPC project lsB06_SUPMOT).

[1] A. Georges, L. De' Medici, J. Mravlje, Annual Reviews of Condensed Matter Physics **4**, 137-178 (2013).
[2] K. Haule and G. Kotliar, New Journal of Physics **11**,

025021 (2009).
[3] J. Mravlje, M. Aichhorn, T. Miyake, K. Haule, G. Kotliar, and A. Georges, Phys. Rev. Lett. **106**, 096401 (2011).
[4] L. de Medici, S. R. Hassan, M. Capone and Xi Dai, Phys. Rev. Lett. **102**, 126401 (2009).
[5] L. de' Medici, G. Giovannetti, and M. Capone, arXiv:1212.3966
[6] G. R. Blake, T. T. M. Palstra, Y. Ren, A. A. Nugroho and A. A. Menovsky, Phys. Rev. Lett. **87**, 245501 (2001).
[7] Z. H. Zhu, F. J. Rueckert, J.I. Budnick, W.A. Hines, M. Jain, H. Zhang, and B. O. Wells, Phys. Rev. B **87**, 195129 (2013).
[8] J.-S. Zhou, C.Q. Jin, Y.W. Long, L.X. Yang, and J.B. Goodenough, Phys. Rev. Lett. **96**, 046408 (2006).
[9] B.L. Chamberland, Solid State Commun. **5**, 663 (1967).
[10] A. J. Williams, A. Gillies, J.P. Attfield, G. Heymann, H. Huppertz, M. J. Martnez-Lope and J. A. Alonso, Phys. Rev. B **73**, 104409 (2006).
[11] A. C. Komarek, T. Mller, M. Isobe, Y. Drees, H. Ulbrich, M. Azuma, M. T. Fernndez-Daz, A. Senyshyn, M. Hoelzel, G. Andr, Y. Ueda, M. Grninger, and M. Braden, Phys. Rev. B **84**, 125114 (2011).
[12] S. V. Streltsov, M. A. Korotin, V. I. Anisimov and D. I. Khomskii, Phys. Rev. B **78**, 054425 (2008).
[13] K. W. Lee and W. E. Pickett, Phys. Rev. B **80**, 125133 (2009).
[14] P. Hohenberg and W. Hohn, Phys. Rev. **136** B864 (1964); W. Kohn and L. J. Sham, Phys. Rev. **140** A1133 (1965).
[15] A. Georges, G. Kotliar, W. Krauth, and M. J. Rozenberg, Rev. Mod. Phys. **68**, 13 (1996).
[16] P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, G. L. Chiarotti, M. Cococcioni, I. Dabo, A. Dal Corso, S. Fabris, G. Fratesi, S. de Gironcoli, R. Gebauer, U. Gerstmann, C. Gougoussis, A. Kokalj, M. Lazzeri, L. Martin-Samos, N. Marzari, F. Mauri, R. Mazzarello, S. Paolini, A. Pasquarello, L. Paulatto, C. Sbraccia, S. Scandolo, G. Sclauzero, A. P. Seitsonen, A. Smogunov, P. Umari, R. M. Wentzcovitch, J. Phys. Condens. Matter **21**, 395502 (2009).
[17] P. Blaha, K. Schwarz, P. Sorantin, and S. B. Trickey, Comput. Phys. Commun. **59**, 399 (1990); K. Schwarz and P. Blaha, Comput. Mater. Sci. **28**, 259 (2003).
[18] A. A. Mostofi, J. R. Yates, Y.-S. Lee, I. Souza, D. Vanderbilt and N. Marzari, Comput. Phys. Commun. **178**, 685 (2008).
[19] M. Ferrero and O. Parcollet, TRIQS: a Toolbox for Research in Interacting Quantum Systems, http://ipht.cea.fr/triqs.
[20] Loig Vaugier, Hong Jiang and Silke Biermann, Phys. Rev. B **86**, 165105 (2012)
[21] M. Caffarel and W. Krauth, Phys. Rev. Lett. **72**, 1545 (1994).
[22] M. Capone, L. de' Medici, and A. Georges, Phys. Rev. B **76**, 245116 (2007).
[23] E. Gull, A. J. Millis, A. I. Lichtenstein, A. N. Rubtsov, M. Troyer, and P. Werner, Rev. Mod. Phys. **83**, 349 (2011).
[24] L. Boehnke, H. Hafermann, M. Ferrero, F. Lechermann, and O. Parcollet, Phys. Rev. B **84**, 075145 (2011).
[25] N. Parragh, A. Toschi, K. Held, and G. Sangiovanni, Phys. Rev. B **86**, 155158
[26] L. De' Medici, J. Mravlje, and A. Georges, Phys. Rev. Lett. **107**, 256401 (2011).
[27] H. A. Jahn and E. Teller, Proc. R. Soc. A 161, 220 (1937).
[28] G. R. Blake and T. T. M. Palstra, Y. Ren, A. A. Nugroho and A. A. Menovsky, Phys. Rev. Lett. **87**, 245501 (2001).
[29] Zhong Fang and Naoto Nagaosa, Phys. Rev. Lett. **93**, 176404 (2004).
[30] K. I. Kugel and D. I. Khomskii, Sov. Phys. Usp. **25**, 231 (1982).
[31] L. Paolasini, R. Caciuffo, A. Sollier, P. Ghigna, and M. Altarelli, Phys. Rev. Lett. **88**, 106403 (2002).
[32] J. Rodrguez-Carvajal, M. Hennion, F. Moussa, A. H. Moudden, L. Pinsard, A. Revcolevschi, Phys. Rev. B **57**, R3189 (1998).
[33] S. Margadonna, G. Karotsis J. Mater. Chem. **17** 2013 (2007); G. Giovannetti, S. Margadonna, J. van den Brink 2008 Phys. Rev. B **77** 075113 (2008).
[34] Y. Ren, T.T.M. Palstra, D.I. Khomskii, E. Pellegrin, A.A. Nugroho, A.A. Menovsky, G.A. Sawatzky, Nature **396** 6710 (1998).
[35] J.B. Goodenough, Magnetism and Chemical Bond (Interscience, New York, 1963).
[36] I. Leonov, N. Binggeli, Dm. Korotin, V. I. Anisimov, N. Stojic and D. Vollhardt, Phys. Rev. Lett. **101**, 096405 (2008).